

Polaron-adsorbate coupling at the TiO₂(110)-carboxylate interface

Article

Published Version

Creative Commons: Attribution 4.0 (CC-BY)

Open Access

Tanner, A. J., Wen, B., Ontaneda, J., Zhang, Y., Grau-Crespo, R. ORCID: <https://orcid.org/0000-0001-8845-1719>, Fielding, H. H., Selloni, A. and Thornton, G. (2021) Polaron-adsorbate coupling at the TiO₂(110)-carboxylate interface. *Journal of Physical Chemistry Letters*, 12 (14). pp. 3571-3576. ISSN 1948-7185 doi: <https://doi.org/10.1021/acs.jpcllett.1c00678> Available at <https://centaur.reading.ac.uk/97417/>

It is advisable to refer to the publisher's version if you intend to cite from the work. See [Guidance on citing](#).

Published version at: <https://doi.org/10.1021/acs.jpcllett.1c00678>

To link to this article DOI: <http://dx.doi.org/10.1021/acs.jpcllett.1c00678>

Publisher: American Chemical Society

All outputs in CentAUR are protected by Intellectual Property Rights law, including copyright law. Copyright and IPR is retained by the creators or other copyright holders. Terms and conditions for use of this material are defined in the [End User Agreement](#).

www.reading.ac.uk/centaur

CentAUR

Central Archive at the University of Reading

Reading's research outputs online

Polaron-Adsorbate Coupling at the TiO₂(110)-Carboxylate Interface

Alex J. Tanner, Bo Wen, Jorge Ontaneda, Yu Zhang, Ricardo Grau-Crespo, Helen H. Fielding, Annabella Selloni, and Geoff Thornton*

Cite This: *J. Phys. Chem. Lett.* 2021, 12, 3571–3576

Read Online


ACCESS |

Metrics & More

Article Recommendations

Supporting Information

ABSTRACT: Understanding how adsorbates influence polaron behavior is of fundamental importance in describing the catalytic properties of TiO₂. Carboxylic acids adsorb readily at TiO₂ surfaces, yet their influence on polaronic states is unknown. Using UV photoemission spectroscopy (UPS), two-photon photoemission spectroscopy (2PPE), and density functional theory (DFT) we show that dissociative adsorption of formic and acetic acids has profound, yet different, effects on the surface density, crystal field, and photoexcitation of polarons in rutile TiO₂(110). We also show that these variations are governed by the contrasting electrostatic properties of the acids, which impacts the extent of polaron–adsorbate coupling. The density of polarons in the surface region increases more in formate-terminated TiO₂(110) relative to acetate. Consequently, increased coupling gives rise to new photoexcitation channels via states 3.83 eV above the Fermi level. The onset of this process is 3.45 eV, likely adding to the catalytic photoyield.

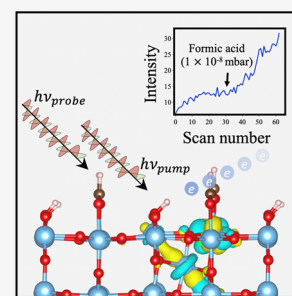

TiO₂ is a versatile, low-cost material for a wide range of light-driven applications such as photovoltaics,¹ water splitting,² and organic photodegradation.^{3–8} It is well known that defects and their associated polarons have a large influence on the activity of these functions, behaving as charge transfer sites and electron traps.^{9–11}

Carboxylic acids are ubiquitous at photocatalytic titania surfaces due to their high affinity for bonding to surface Ti atoms.¹² Formic (HCOOH) and acetic (CH₃COOH) acid represent the simplest carboxylic acid analogues. Their adsorption on TiO₂ results in the formation of atomic-scale ordered overlayers at the ultrahigh vacuum (UHV), liquid and atmospheric interface, which can be observed by scanning tunneling microscopy.^{12–16} At the rutile TiO₂(110) surface specifically, the dominant adsorption configuration of these acids consists of bidentate-bound carboxylates (RCOO[−]) at five-coordinate titanium atoms (Ti_{5c}) along the [001] direction.¹⁷ This is accompanied by the protonation of bridging O (OH_b) and the formation of a (2 × 1) majority phase adsorption structure (see Figure 1(a)). A minority carboxylate component is also present, which is a monodentate species oriented perpendicular to [001] and accounts for up to 1/3 of the interface.^{14,18–20} Formic and acetic acid adsorption saturates at ~0.5 ML in UHV at 298 K, where a monolayer corresponds to the number of surface unit cells. The two terminations are denoted FA- and AA-R110, respectively.

Defects in rutile TiO₂, namely surface oxygen vacancies (O_{vac}) and bulk interstitial titanium atoms (Ti_{int}), give rise to excess electrons in localized polaronic states.²¹ The energy levels of the electron polarons represent what are commonly referred to as the band gap states (BGS) of reduced TiO₂, which are detectable at ~1.0 eV binding energy (BE) in UV photoelectron spectroscopy (UPS).^{22,23} Formally, the BGS are

Ti 3d_{xy} in character. This results from the Jahn–Teller splitting of Ti_{3d} atomic states in the pseudo-octahedral crystal field of rutile, which gives rise to orbitals of t_{2g}- and e_g-like symmetry.^{10,24,25} Polarons at surface O_{vac} readily react with water to form OH_b,⁹ resulting in a small increase in the UPS BGS signal without altering the BE.²⁶ This indicates that OH_b triggers deeper lying polarons to redistribute toward the surface, a mechanism that is also supported by density functional theory (DFT) calculations.^{26,27}

Although electron polaronic states have been studied extensively, it is only recently that pump–probe studies have allowed access to their excited states. One technique employed is two-photon photoemission spectroscopy (2PPE).^{28–30} At reduced and hydroxylated TiO₂(110) surfaces, 2PPE spectra are dominated by a t_{2g} → t_{2g} excitation feature where the excited state lies ~2.6–2.8 eV above E_F.^{28,30–32} The oscillator strength of this excitation is strongly dependent on the orientation of the electric field vector. This increases when the scattering plane is perpendicular to the [001] crystal azimuth, (*p*-[001]).^{28–30,32} In contrast, a weaker feature is observed when the scattering plane is parallel to the [001] azimuth, (*s*-[001]).^{29,30} Furthermore, it has been shown that water and methanol adsorption influences this channel, altering the orbital character and resulting in an enhancement of the t_{2g} → t_{2g} excitation oscillator strength.^{27,33–35} Despite these recent advances, the impact of carboxylates on electron polaronic

Received: March 2, 2021

Accepted: March 31, 2021

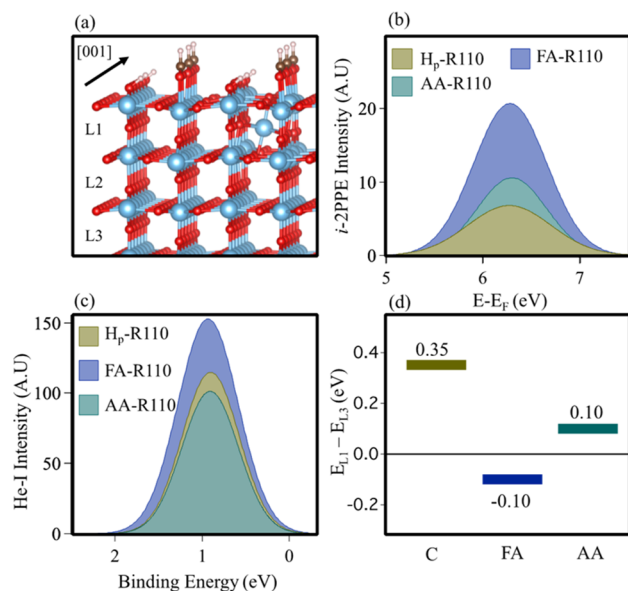


Figure 1. (a) Rutile TiO₂(110) model showing the majority phase (2 × 1) formate and OH_b overlayer resulting from dissociative chemisorption of formic acid. An interstitial titanium atom (Ti_{int}) is shown at position L1. Blue, red, brown, and white spheres represent Ti, O, C, and H, respectively. (b) Comparison of the dominant $t_{2g} \rightarrow t_{2g}$ transition in the 2PPE spectra of the H_p-R110, FA-R110, and AA-R110 terminations at a photon energy of 3.54 eV (p -[001], 350 nm). Incoherent (i) features are produced according to the equation $E - E_F = h\nu_{\text{probe}} + E_{\text{intermediate}}$. Spectra were produced continuously at constant laser power with *in situ* gas-phase dosing. Peaks are isolated via the method described in SI Section S2. (c) Comparison of the BGS region in the UPS (He-I, 21.2 eV) spectra on the H_p-R110, FA-R110, and AA-R110 surfaces. Peaks are isolated via the method described in SI Section S2. (d) Bar chart showing the difference in energy (ΔE) between a surface (L1) and bulk (L3) Ti_{int} in the clean, formate, and acetate termination of rutile TiO₂(110), calculated with HSE06 DFT. A positive ΔE means that L1 is energetically less stable than L3. See details in Table S1.

states remains unknown. This understanding is potentially valuable for several technologies since carboxylates serve as the most important anchoring group for the functionalization of TiO₂ surfaces. In this Letter, we describe a UPS, 2PPE, and DFT study that investigates the modification of electron polarons by carboxylates and their subsequent photoexcitation.

Features in 2PPE spectra are most commonly produced as a result of coherent (simultaneous two-photon excitation of an occupied state) or incoherent (two sequential one-photon excitations via an intermediate state) processes.³⁶ At resonant photon energy conditions, optimal coherence between an initial and intermediate state energy results in an increase in the 2PPE intensity.³⁶ In reduced and hydroxylated TiO₂(110) (see SI for preparation methods), the resonant photon energy for the $t_{2g} \rightarrow t_{2g}$ excitation is known to be ~ 3.54 eV (350 nm).²⁸ In Figure 1(b), this resonance was monitored (p -[001], 3.54 eV, 350 nm) as a reduced rutile TiO₂(110) sample (R-R110) partially hydroxylated in UHV (H_p-R110, ~ 0.05 ML) and was sequentially exposed to gas-phase acid. This was performed *in situ* until the saturation level (~ 0.5 ML) was reached. The increase of the 2PPE resonance via hydroxylation of O_{vac} has been discussed in prior work.^{27,28,30,31} Upon creation of FA- and AA-R110, we find that the dominant incoherent process is approximately 3× and 2× larger, respectively (taken by peak area). An example of spectral

evolution throughout this experiment is also shown in the Supporting Information (SI) Figure S1. In a similar framework, the BGS is monitored via UPS (He-I, 21.2 eV) and increases by a factor of ~ 1.4 following formate adsorption. Following acetate adsorption the BGS area is ~ 0.9 times the size, consistent with previous measurements.^{37–39} This is represented in Figure 1(c). In Figures 1(b) and (c) the peaks are isolated by removing backgrounds and are fit with Gaussian distributions (see SI, Figure S2). The difference in trend between the UPS and 2PPE data for AA-R110 is likely due to the escape depth of the two techniques (~ 1 and 5 nm, for UPS and 2PPE, respectively).⁴⁰

To further understand these observations we carried out DFT calculations (see SI for methods) using the HSE06 hybrid functional,⁴¹ which describes polaronic states in TiO₂ with good accuracy.^{30,32} Ti_{int} defects were used as the source of excess electrons, and the location of Ti_{int} was varied from the immediate subsurface (L1) to two (L2) and three (L3) layers below the surface in a (4 × 2) 6-trilayers slab. Previous DFT work showed that the most stable Ti_{int} location changes upon water and methanol adsorption.²⁷ Here, we determine the relative energies of Ti_{int} at clean (C) TiO₂(110) and at the surface covered by a (2 × 1) formate or acetate monolayer. The relative stabilities of different Ti_{int} locations change significantly in the presence of a carboxylate monolayer. At the adsorbate-free surface, the most stable Ti_{int} site is L2, which is 0.46 (0.11) eV more stable than L1 (L3). In contrast, at the formate-covered surface Ti_{int} at L2 is only 0.08 eV more stable than at L1 (and 0.18 eV more stable than at L3). In the presence of an acetate monolayer, L2 and L3 are 0.09 and 0.10 eV more stable, respectively, than L1. The energetics of surface Ti_{int} following carboxylate adsorption is summarized in Figure 1(d), which shows the energy (ΔE) difference between surface (L1) and bulk (L3) Ti_{int} locations (see full details in SI, Table S1). Together, the UPS, 2PPE, and DFT results indicate that formate adsorption leads to the redistribution of polarons toward the surface of TiO₂(110) through the mechanism of Ti_{int} migration. The data also show that this effect is less pronounced in the acetate termination.

On FA-R110, polaron photoexcitation was further studied by rotating the electric field vector by 90° relative to the crystal azimuth (s -[001]). Figure 2(a) follows the 2PPE spectrum (3.54 eV, 350 nm) as formic acid is dosed directly onto R-R110, allowing contributions from initially reactive O_{vac} (~ 0.1 ML) sites to be separated.¹⁹ At ~ 0.1 ML coverage the spectrum largely resembles that of R-R110, evidencing a slight increase in the $t_{2g} \rightarrow t_{2g}$ feature, labeled feature 1. Following saturation of the Ti_{Sc} rows (~ 0.5 ML), an additional feature, labeled feature 2, becomes clear. The apparent shift of feature 1 at this coverage is due to its convolution with feature 2. The inset shows the difference spectrum between the ~ 0.5 ML coverage and ~ 0.1 ML coverage, where the appearance of feature 2 is clear. The dependence of feature 2 on the ~ 0.5 ML coverage of formate was additionally confirmed by inducing formate decomposition reactions (see SI, Figure S3).

The photon energy dependence of feature 2 was also examined and is shown in Figure 2(b). Feature 2 occurs close to the $E_F + 2h\nu$ maxima of the 2PPE spectra and has an onset $h\nu$ of ~ 3.45 eV (360 nm). 2PPE spectra with $h\nu > 3.54$ eV (350 nm) show that feature 2 becomes more prominent in the spectra as feature 1 is less resonant. It is also observed that feature 2 is visible at much higher photon energies compared to feature 1. Figure 2(c) shows the plot of final-state energy (E

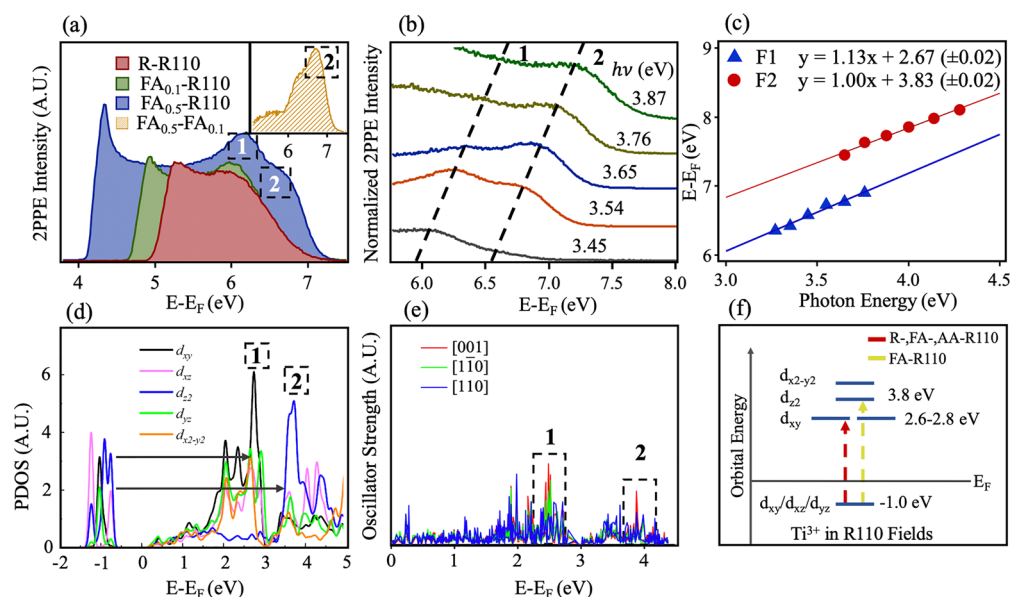


Figure 2. (a) 2PPE spectra ($h\nu = 3.54$ eV, 350 nm, s -[001]) of a reduced rutile $\text{TiO}_2(110)$ sample (R-R110) taken continuously as formic acid is dosed *in situ*. The subscript number in the legend signifies the approximate ML coverage of the formate. Numbers in dashed boxes represent the position and label of the respective features. Feature 1 denotes the previously identified $t_{2g} \rightarrow t_{2g}$ transition. The inset shows the spectrum with 0.5 ML coverage minus that at 0.1 ML coverage. (b) 2PPE spectra of selected regions containing features 1 and 2, with photon energies ($h\nu = 3.44$ – 3.87 eV, 360–320 nm), s -[001]. Spectra are normalized to fit the figure window for clarity. (c) Plot of the photon energy dependence of the two fitted peaks in FA_{0.5}-R110 (see Section S2 in the SI for the fitting procedure) given by the equation for the incoherent process, $E - E_F = h\nu_{\text{probe}} + E_{\text{intermediate}}$. (d) Computed PDOS of Ti^{3+} states on FA-R110, with Ti_{int} located at L1. Peaks in the conduction band are labeled to correspond to features 1 and 2. (e) Computed oscillator strengths for transitions from BGS to the conduction band in the same system considered in (d). Red [001], green [110], and blue [110] represent directions of transition dipole moments. Peaks in the oscillator strengths are labeled that coincide with features 1 and 2. (f) Scheme showing the transitions of features 1 and 2. Feature 2 represents a $t_{2g} \rightarrow e_g$ excitation. A red arrow represents transitions observed in R-, FA-, and AA-R110. A yellow arrow represents transitions observed in FA-R110 only.

$-E_F$) versus photon energy (eV). It is well understood that in these plots incoherent and coherent processes produce gradients of 1 and 2, respectively.³⁶ Both features are produced via an incoherent process where the excited state lies ~ 2.7 and 3.8 eV above E_F for features 1 and 2, respectively (given by the y -intercepts). In both plots, photon energies are chosen so as to minimize overlap of the features.

DFT is again used to obtain insight into the origin of the observations. Figure 2(d) shows the partial density of states (PDOS) of excess electrons from Ti_{int} at L1 of a $\text{TiO}_2(110)$ surface with a (2×1) formate overlayer. The distribution has been separated into individual d -orbital contributions. The excited state energies of features 1 and 2 are represented clearly by significant density of states in the Ti^{3+} conduction band having d_{xy} and d_z^2 orbital character, respectively. Figure 2(e) shows the results of associated oscillator strength calculations for BGS to conduction band excitation. Peaks corresponding to both features are observed. The transition dipole moment for feature 1 lies in both the [001] and [110] direction in this environment. In contrast, a transition dipole moment for feature 2 is present only in the [001] direction, explaining the observed polarization dependence. Features 1 and 2 therefore represent an excitation from occupied states t_{2g} -like in character to unoccupied states of t_{2g} - and e_g -like character, respectively. A schematic of this excitation scheme is shown in Figure 2(f). Extended PDOS and oscillator strength calculations (Ti_{int} L1–L3) showing the effects of carboxylates on polaron orbital energies are given in the Figure S4.

Adsorption of the carboxylates leads to a pronounced reduction in the workfunction (5.1, 4.4, and 4.2 eV for R-, FA-, and AA-R110, respectively), which has implications for the

2PPE spectra. Specifically, this results in an enlarged 2PPE spectral window and an increased scope to study lower energy photoexcitation processes. However, at higher photon energies lower energy 2PPE features are often imperceptible due to dominating coherent valence band contributions, as well as single-photon photoemission from states near E_F . Figure 3(a) shows the 2PPE spectra of AA-R110 (p -[001], 3.75–3.35 eV, 330–370 nm). As expected in this orientation, a strong peak associated with feature 1 is present. At ~ 5.2 eV above E_F a broad feature is present that is unaffected by the shifting photon energy. This feature is also present in the 2PPE spectra (p -[001]) of FA-R110 (see Figure S5). We assign this distribution to Auger electrons, ejected from the BGS via the multiphoton excitation and recombination of valence band electrons. This feature also acts as a normalization point. The Auger feature is discussed in further detail in Figure S6.

Figure 3(b) compares the wavelength-dependent intensity of feature 1 in FA- and AA-R110 (p -[001]). This comparison was made by normalizing to the Auger feature, which is present in both terminations. FA-R110 has an increased intensity of feature 1 relative to AA-R110 in all wavelengths tested. Furthermore, in both terminations 2PPE with $h\nu = 3.54$ eV (350 nm) produces the most intense peak, as for the adsorbate-free surface. This demonstrates that there is no distinct adsorbate-induced splitting of the occupied and unoccupied t_{2g} orbitals undergoing excitation.

There are a number of potential reasons for the differences in spectral intensity for the two adsorbates, with Ti_{int} migration and photoelectron attenuation important factors. However, DFT results suggest an additional important element. Due to the electron-donating effects of the methyl substituent, acetate

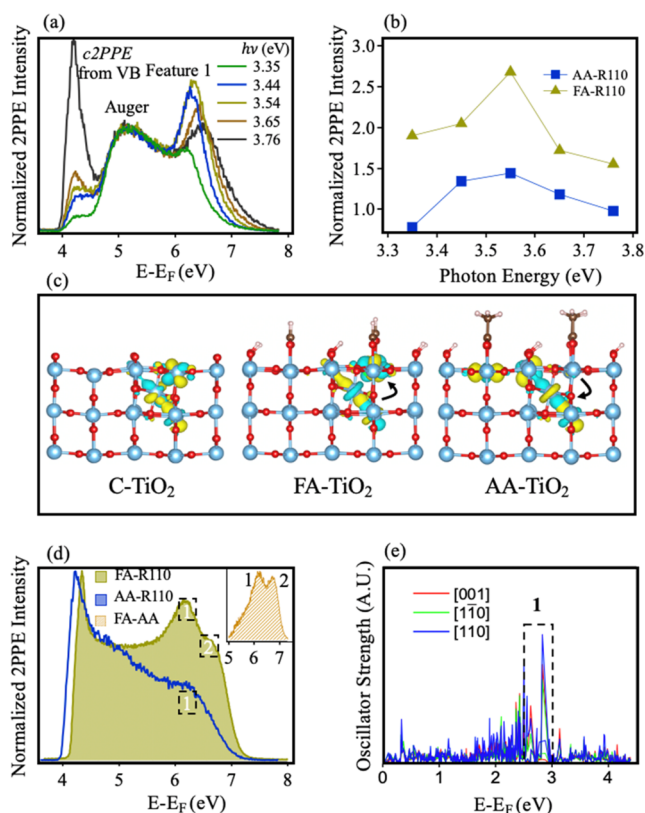


Figure 3. (a) 2PPE spectra ($h\nu = 3.35\text{--}3.75$ eV, 370–330 nm, p -[001]) measured from AA-R110. Three features corresponding to feature 1, Auger electrons, and valence band coherent 2PPE (c2PPE) from TiO_2 are labeled. Spectra are normalized to the Auger feature peak intensity. (b) Peak intensity of feature 1 between ($h\nu = 3.35\text{--}3.75$ eV, 370–330 nm, p -[001]), normalized to the Auger feature, for both FA-R110 and AA-R110. (c) Spin density contour of BGS for Ti_{int} at the L1 site in the C-R110, FA-R110, and AA-R110 terminations. Arrows showing electron transfer to represent the relative attractive and repulsive properties of acid adsorbates relative to the clean surface. The red, light blue, brown, and pink spheres represent Ti, O, C, and H atoms, respectively. (d) Comparison of FA-R110 and AA-R110 2PPE (3.54 eV photons, 350 nm, s -[001]). The inset shows the difference spectrum between the two terminations. (e) Calculated oscillator strengths from BGS to the conduction band with L1 Ti_{int} in the acetate-terminated system. Red [001], green [110], and blue [110] represent directions of the transition dipole moments.

repels excess electrons from the adsorbate. This is in contrast to formate, which attracts them. This is evidenced in Figure 3(c), where the spin density contour of four distinctly located excess electrons in C-, FA-, and AA-R110 are shown. Further modifications by the adsorbates can also be seen in this model. Specifically, in C-R110 the occupied states contain only orbitals of t_{2g} -like character. However, following adsorption of FA and AA, new orbital characters arise. Focusing on the excess electron localized at Ti_{int} in FA- and AA-R110, a d_z^2 -like orbital character can be identified. This change can be understood as an adsorbate-induced local crystal field. Specifically, the original octahedral crystal field is tilted into a trigonal prismatic field. In this new field, d_z^2 orbitals are lower in energy than the other 3d orbitals and subsequently appear in the spin density contour (Figure 3(c)) and PDOS (Figure 2(d)) (see also Figure S4). The density of those electrons in a trigonal prismatic field is governed by the electronegativity of

the acid. In FA-R110, electrons are attracted away from Ti_{int} resulting in a higher proportion of surface localized t_{2g} -like states compared to AA-R110. These surface states can undergo additional couplings between t_{2g} and d_z^2 , which result in the appearance of feature 2 in the 2PPE spectra of FA-R110 and its absence in AA-R110. This comparison is shown in Figure 3(d) (s -[001], 3.54 eV, 350 nm, see Figure S7 for further AA-R110 spectra). The absence of feature 2 in the 2PPE spectra of AA-R110 is also corroborated by the results of oscillator strength calculations in Figure 3(e), where no clear peaks at the position of feature 2 are observed (compare Figures 2(e) and 3(e)). Furthermore, we assign feature 2 to states localized at the surface based on oscillator strength calculations, which show that feature 2 is present only in the formate termination with Ti_{int} located at L1 and L2 (see Figure S4).

In summary, we have established that the facile formation of formate and acetate overlayers has dramatic, yet differing, implications for the behavior of polaronic states in rutile $\text{TiO}_2(110)$. Carboxylate adsorption leads to polaron redistribution toward the surface, driven by the migration of Ti_{int} . This occurs more prominently in FA-R110, compared to AA-R110. Adsorbates subsequently couple with polaronic states to form unique crystal fields which alters the orbital character. The extent of this coupling is determined by the electrostatic properties of the carboxylate. For example, at the formate termination, polarons are attracted toward the adsorbate, increasing the oscillator strength of higher energy transitions. Specifically, polarons undergo photoexcitation via an intermediate state ~ 3.83 eV above E_{F} , characterized as a $t_{2g} \rightarrow e_g$ transition. It is also observed that the 2PPE spectra of both carboxylate-terminated $\text{TiO}_2(110)$ contain significant contributions from an Auger feature. Understanding how polarons interact with adsorbates is crucial if we are to describe the role of defects in TiO_2 catalysis. This work provides an understanding of how carboxylates may enhance the activity of polarons by increasing their density at the surface, protecting them against oxidation (see Figure S8) and giving access to alternative photoexcitation channels.

■ ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acs.jpcllett.1c00678>.

Experimental details, computational details, and Figures S1–S8, showing further DFT calculations and PES spectra with extended discussion (PDF)

■ AUTHOR INFORMATION

Corresponding Author

Geoff Thornton – Department of Chemistry, University College London, London WC1H 0AJ, United Kingdom; London Centre for Nanotechnology, University College London, London WC1H 0AH, United Kingdom; orcid.org/0000-0002-1616-5606; Email: g.thornton@ucl.ac.uk

Authors

Alex J. Tanner – Department of Chemistry, University College London, London WC1H 0AJ, United Kingdom; London Centre for Nanotechnology, University College London, London WC1H 0AH, United Kingdom

Bo Wen – Department of Chemistry, Princeton University, Princeton, New Jersey 08540, United States; orcid.org/0000-0001-7252-918X

Jorge Ontaneda – Department of Chemistry, University of Reading, Whiteknights, Reading RG6 6AX, United Kingdom; orcid.org/0000-0003-1538-365X

Yu Zhang – Department of Chemistry, University College London, London WC1H 0AJ, United Kingdom; London Centre for Nanotechnology, University College London, London WC1H 0AH, United Kingdom; orcid.org/0000-0001-6184-4870

Ricardo Grau-Crespo – Department of Chemistry, University of Reading, Whiteknights, Reading RG6 6AX, United Kingdom; orcid.org/0000-0001-8845-1719

Helen H. Fielding – Department of Chemistry, University College London, London WC1H 0AJ, United Kingdom; orcid.org/0000-0003-1572-0070

Annabella Selloni – Department of Chemistry, Princeton University, Princeton, New Jersey 08540, United States; orcid.org/0000-0001-5896-3158

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acs.jpcllett.1c00678>

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

We thank River Riley, Omri Tau and Robin Kerr for their assistance in maintaining stable laser and UHV conditions. This work was supported by the European Research Council Advanced Grant ENERGYSURF (G.T.), EPSRC (U.K.) (EP/D068673/1), EU COST Action CM1104, and the Royal Society (U.K.) through a Wolfson Research Merit Award to G.T. The research is supported by the TIGRESS high-performance computer center at Princeton University. B.W. and A.S. acknowledge the support of DoE-BES, Division of Chemical Sciences, Geosciences and Biosciences, under award DESC0007347.

REFERENCES

- O'Regan, B.; Grätzel, M. A Low-Cost, High-Efficiency Solar Cell Based on Dye-Sensitized Colloidal TiO₂ Films. *Nature* **1991**, *353* (6346), 737–740.
- Fujishima, A.; Honda, K. Electrochemical Photolysis of Water at a Semiconductor Electrode. *Nature* **1972**, *238* (5358), 37–38.
- Onishi, H.; Aruga, T.; Iwasawa, Y. Catalytic Reactions on a Metal Oxide Single Crystal: Switchover of the Reaction Paths in Formic Acid Decomposition on Titanium Dioxide TiO₂(110). *J. Am. Chem. Soc.* **1993**, *115* (22), 10460–10461.
- Linsebigler, A. L.; Lu, G.; Yates, J. T. Photocatalysis on TiO₂ Surfaces: Principles, Mechanisms, and Selected Results. *Chem. Rev.* **1995**, *95* (3), 735–758.
- Henderson, M. A. Complexity in the Decomposition of Formic Acid on the TiO₂(110) Surface. *J. Phys. Chem. B* **1997**, *101* (2), 221–229.
- Xu, M.; Gao, Y.; Moreno, E. M.; Kunst, M.; Muhler, M.; Wang, Y.; Idriss, H.; Wöll, C. Photocatalytic Activity of Bulk TiO₂ Anatase and Rutile Single Crystals Using Infrared Absorption Spectroscopy. *Phys. Rev. Lett.* **2011**, *106* (13), 138302.
- Henderson, M. A.; White, M. J.; Uetsuka, H.; Onishi, H. Photochemical Charge Transfer and Trapping at the Interface Between an Organic Adlayer and an Oxide Semiconductor. *J. Am. Chem. Soc.* **2003**, *125* (49), 14974–14975.
- Sandell, A.; Ragazzon, D.; Schaefer, A.; Farstad, M. H.; Borg, A. Photochemistry of Carboxylate on TiO₂(110) Studied with Synchrotron Radiation Photoelectron Spectroscopy. *Langmuir* **2016**, *32* (44), 11456–11464.
- Bikondoa, O.; Pang, C. L.; Ithnin, R.; Muryn, C. A.; Onishi, H.; Thornton, G. Direct Visualization of Defect-Mediated Dissociation of Water on TiO₂(110). *Nat. Mater.* **2006**, *5* (3), 189–192.
- Papageorgiou, A. C.; Beglitis, N. S.; Pang, C. L.; Teobaldi, G.; Cabailh, G.; Chen, Q.; Fisher, A. J.; Hofer, W. A.; Thornton, G. Electron Traps and Their Effect on the Surface Chemistry of TiO₂(110). *Proc. Natl. Acad. Sci. U. S. A.* **2010**, *107* (6), 2391–2396.
- Leijtens, T.; Eperon, G. E.; Pathak, S.; Abate, A.; Lee, M. M.; Snaith, H. J. Overcoming Ultraviolet Light Instability of Sensitized TiO₂ with Meso-Superstructured Organometal Tri-Halide Perovskite Solar Cells. *Nat. Commun.* **2013**, *4* (1), 2885.
- Balajka, J.; Hines, M. A.; DeBenedetti, W. J. I.; Komora, M.; Pavelec, J.; Schmid, M.; Diebold, U. High-Affinity Adsorption Leads to Molecularly Ordered Interfaces on TiO₂ in Air and Solution. *Science* **2018**, *361* (6404), 786–789.
- Grinter, D. C.; Nicotra, M.; Thornton, G. Acetic Acid Adsorption on Anatase TiO₂(101). *J. Phys. Chem. C* **2012**, *116* (21), 11643–11651.
- Grinter, D. C.; Woolcot, T.; Pang, C. L.; Thornton, G. Ordered Carboxylates on TiO₂(110) Formed at Aqueous Interfaces. *J. Phys. Chem. Lett.* **2014**, *5* (24), 4265–4269.
- Diebold, U. The Surface Science of Titanium Dioxide. *Surf. Sci. Rep.* **2003**, *48* (5–8), 53–229.
- Wang, Y.; Wen, B.; Dahal, A.; Kimmel, G. A.; Rousseau, R.; Selloni, A.; Petrik, N. G.; Dohnálek, Z. Binding of Formic Acid on Anatase TiO₂(101). *J. Phys. Chem. C* **2020**, *124* (37), 20228–20239.
- Pang, C. L.; Lindsay, R.; Thornton, G. Structure of Clean and Adsorbate-Covered Single-Crystal Rutile TiO₂ Surfaces. *Chem. Rev.* **2013**, *113* (6), 3887–3948.
- Dover, C. M.; Grinter, D. C.; Yim, C. M.; Muryn, C. A.; Bluhm, H.; Salmeron, M.; Thornton, G. Orientation of Acetic Acid Hydrogen Bonded to Acetate Terminated TiO₂(110). *Surf. Sci.* **2020**, *699*, 121628.
- Hayden, B. E.; King, A.; Newton, M. A. Fourier Transform Reflection–Absorption IR Spectroscopy Study of Formate Adsorption on TiO₂(110). *J. Phys. Chem. B* **1999**, *103* (1), 203–208.
- Lun Pang, C.; Lindsay, R.; Thornton, G. Chemical Reactions on Rutile TiO₂(110). *Chem. Soc. Rev.* **2008**, *37* (10), 2328–2353.
- Yim, C. M.; Watkins, M. B.; Wolf, M. J.; Pang, C. L.; Hermansson, K.; Thornton, G. Engineering Polarons at a Metal Oxide Surface. *Phys. Rev. Lett.* **2016**, *117* (11), 116402.
- Yim, C. M.; Pang, C. L.; Thornton, G. Oxygen Vacancy Origin of the Surface Band-Gap State of TiO₂(110). *Phys. Rev. Lett.* **2010**, *104* (3), 036806.
- Wendt, S.; Sprunger, P. T.; Lira, E.; Madsen, G. K. H.; Li, Z.; Hansen, J. Ø.; Matthiesen, J.; Blekinge-Rasmussen, A.; Lægsgaard, E.; Hammer, B.; et al. The Role of Interstitial Sites in the Ti_{3d} Defect State in the Band Gap of Titania. *Science* **2008**, *320* (5884), 1755–1759.
- Setvín, M.; Franchini, C.; Hao, X.; Schmid, M.; Janotti, A.; Kaltak, M.; Van de Walle, C. G.; Kresse, G.; Diebold, U. Direct View at Excess Electrons in TiO₂ Rutile and Anatase. *Phys. Rev. Lett.* **2014**, *113* (8), 086402.
- Yang, S.; Brant, A. T.; Giles, N. C.; Halliburton, L. E. Intrinsic Small Polarons in Rutile TiO₂. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2013**, *87* (12), 125201.
- Yim, C. M.; Chen, J.; Zhang, Y.; Shaw, B.-J.; Pang, C. L.; Grinter, D. C.; Bluhm, H.; Salmeron, M.; Muryn, C. A.; Michaelides, A.; et al. Visualization of Water-Induced Surface Segregation of Polarons on Rutile TiO₂(110). *J. Phys. Chem. Lett.* **2018**, *9* (17), 4865–4871.
- Wen, B.; Yin, W.-J.; Selloni, A.; Liu, L.-M. Defects, Adsorbates, and Photoactivity of Rutile TiO₂(110): Insight by First-Principles Calculations. *J. Phys. Chem. Lett.* **2018**, *9* (18), 5281–5287.

(28) Zhang, Y.; Payne, D. T.; Pang, C. L.; Fielding, H. H.; Thornton, G. Non-Band-Gap Photoexcitation of Hydroxylated TiO₂. *J. Phys. Chem. Lett.* **2015**, *6* (17), 3391–3395.

(29) Argondizzo, A.; Cui, X.; Wang, C.; Sun, H.; Shang, H.; Zhao, J.; Petek, H. Ultrafast Multiphoton Pump-Probe Photoemission Excitation Pathways in Rutile TiO₂(110). *Phys. Rev. B: Condens. Matter Mater. Phys.* **2015**, *91* (15), 155429.

(30) Wang, Z.; Wen, B.; Hao, Q.; Liu, L.-M.; Zhou, C.; Mao, X.; Lang, X.; Yin, W.-J.; Dai, D.; Selloni, A.; et al. Localized Excitation of Ti³⁺ Ions in the Photoabsorption and Photocatalytic Activity of Reduced Rutile TiO₂. *J. Am. Chem. Soc.* **2015**, *137* (28), 9146–9152.

(31) Argondizzo, A.; Tan, S.; Petek, H. Resonant Two-Photon Photoemission From Ti_{3d} Defect States of TiO₂(110) Revisited. *J. Phys. Chem. C* **2016**, *120* (24), 12959–12966.

(32) Wen, B.; Hao, Q.; Yin, W.-J.; Zhang, L.; Wang, Z.; Wang, T.; Zhou, C.; Selloni, A.; Yang, X.; Liu, L.-M. Electronic Structure and Photoabsorption of Ti³⁺ Ions in Reduced Anatase and Rutile TiO₂. *Phys. Chem. Chem. Phys.* **2018**, *20* (26), 17658–17665.

(33) Wang, Z.-Q.; Hao, Q.-Q.; Mao, X.-C.; Zhou, C.-Y.; Ma, Z.-B.; Ren, Z.-F.; Dai, D.-X.; Yang, X.-M. Characterization of the Excited State on Methanol/TiO₂(110) Interface. *Chin. J. Chem. Phys.* **2015**, *28* (2), 123–127.

(34) Onda, K.; Li, B.; Zhao, J.; Petek, H. The Electronic Structure of Methanol Covered TiO₂(110) Surfaces. *Surf. Sci.* **2005**, *593* (1–3), 32–37.

(35) Payne, D. T.; Zhang, Y.; Pang, C. L.; Fielding, H. H.; Thornton, G. Coverage-Dependent Two-Photon Photoexcitation at the H₂O/TiO₂ Interface. *Surf. Sci.* **2016**, *652* (C), 189–194.

(36) Ueba, H.; Gumhalter, B. Theory of Two-Photon Photoemission Spectroscopy of Surfaces. *Prog. Surf. Sci.* **2007**, *82* (4–6), 193–223.

(37) Tao, J.; Luttrell, T.; Bylisma, J.; Batzill, M. Adsorption of Acetic Acid on Rutile TiO₂(110) vs (011)-2 × 1 Surfaces. *J. Phys. Chem. C* **2011**, *115* (8), 3434–3442.

(38) Tao, J.; Batzill, M. Role of Surface Structure on the Charge Trapping in TiO₂ Photocatalysts. *J. Phys. Chem. Lett.* **2010**, *1* (21), 3200–3206.

(39) Cocks, I. D.; Guo, Q.; Patel, R.; Williams, E. M.; Roman, E.; de Segovia, J. L. The Structure of TiO₂(110) (1 × 1) and (1 × 2) Surfaces with Acetic Acid Adsorption — a PES Study. *Surf. Sci.* **1997**, *377–379*, 135–139.

(40) Woodruff, D. P. *Modern Techniques of Surface Science*; Cambridge University Press: 2016.

(41) Heyd, J.; Scuseria, G. E.; Ernzerhof, M. Hybrid Functionals Based on a Screened Coulomb Potential. *J. Chem. Phys.* **2003**, *118* (18), 8207–8215.